

## Flexural Behavior of Self Compacting High Strength Fiber Reinforced Concrete (SCHSFRC)

Vinayak B. Jatale\*, M. N. Mangulkar\*\*

\*( PG Student, Department of Civil Engineering, MGM's Jawaharlal Nehru Engineering College, Aurangabad/ Dr. B.A. Marathwada University, Aurangabad, India)

\*\* (Assistant Professor, Department of Civil Engineering, MGM's Jawaharlal Nehru Engineering College, Aurangabad/ Dr. B.A. Marathwada University, Aurangabad, India)

### ABSTRACT

In this experimental study the changes on some mechanical properties of self compacting concrete specimen produced by silica fume, metakaolin, fly ash and steel fibers were investigated. The main objective of this is to obtain ductile Self Compacting High Strength Concrete (SCHSC) which flows under its own weight and homogeneity while completely filling any formwork and passing around congested reinforcement. The Self Compacting High Strength Concrete produced by using silica fume, metakaolin, fly ash, steel fibers and Polycarboxylate ether base superplasticizer. Three types of steel fibers were used in the experiments and volume fractions of steel fiber were 0.5% to 4.0 %. Addition of silica fume, metakaolin and fly ash into the concrete were 2.5 %, 2.5 % and 10 % by weight of cement content respectively. Water/cement ratio was 0.29. Flexural strength test were made on hardened concrete specimens.

**Keywords** - Fly Ash, Flexural strength High Strength Concrete (HSC), High Strength Fiber Reinforced Concrete (HSFRC), Metakaolin, Silica fume, Steel Fibres.

### I. INTRODUCTION

Construction of durable concrete structures requires skilled labor for placing and compacting concrete. Self Compacting Concrete achieves this by its unique fresh state properties. In the plastic state, it flows under its own weight and homogeneity while completely filling any formwork and passing around congested reinforcement. In the hardened state, it equals or excels standard concrete with respect to strength and durability. This work is aimed to study the performance of steel fiber reinforced self compacting concrete as plain self compacting concrete is studied in depth but the fiber reinforced self compacting concrete is not studied to that extent. The main objective of this study is to optimize the Steel Fiber Reinforced Self Compacting High Strength Concrete (SFRSCHSC) in the hardened state. But the literature indicates that some studies are available on plain SCC but sufficient literature is not available on Steel Fiber Reinforced Self Compacting

High Strength Concrete (SFRSCHSC) with different mineral admixtures. Hence an attempt is made in this work to study the mechanical properties of both plain Self Compacting High Strength Concrete (SCHSC) and SFRSCC.

### II. MATERIAL USED

#### 2.1 Cement

Ordinary Portland Cement of 53 Grade conforming to IS: 12269-1987 was used in the investigation. The specific gravity of cement was 3.10.

#### 2.2 Coarse Aggregate

Crushed stone metal with a maximum size of 12.5 mm from a local source having the specific gravity of 2.7 conforming to IS: 383-1970 was used.

#### 2.3 Fine Aggregate

Locally available river sand passing through 4.75 mm IS sieve conforming to grading zone-II of IS: 383-1970 was used. The specific gravity of fine aggregate was 2.54.

#### 2.4 Silica fume

The American Concrete Institute (ACI) defines silica fume as "very fine noncrystalline silica produced in electric arc furnace as a byproduct of production of elemental silicon or alloys containing silicon". Silica fume is also known as micro silica, condensed silica fume, volatilized silica or silica dust. The physical properties and chemical composition of Silica fume are shown in table 2.1 and table 2.2 respectively.

#### 2.5 Metakaolin

Metakaolin is not a byproduct. It is obtained by the calcinations of pure or refined Kaolinite clay at a temperature between 650<sup>0</sup> C and 850<sup>0</sup>C, followed by grinding to achieve a fineness of 700-900 m<sup>2</sup>/kg. Metakaolin is a high quality pozzolonic material, which is blended with cement in order to improve the durability of concrete. The physical properties and chemical composition of metakaolin are shown in table 2.1 and table 2.2 respectively.

**Table 2.1: Physical Properties of Silica Fume & Metakaolin**

Property	Specific Gravity	Bulk Density (g/cm <sup>3</sup> )	Physical Form	Colour
Silica Fume	2.27	0.13 to 0.43	Powder	White
Metakaolin	2.60	0.3 to 0.4	Powder	Off White

**Table 2.2: Chemical Composition of Silica Fume & Metakaolin**

Oxide	Si O <sub>2</sub>	Al <sub>2</sub> O <sub>3</sub>	Fe <sub>2</sub> O <sub>3</sub>	CaO	MgO	K <sub>2</sub> O	SO <sub>3</sub>	Na <sub>2</sub> O	LOI
% by mass	92.1	0.5	1.4	0.5	0.3	0.7	0.0	0.3	2.8
	51.52	40.18	1.23	2.0	0.12	0.53	0.0	0.08	2.01

### 2.6 Fly Ash

Fly ash is available in dry powder form and is procured from Dirk India Pvt. Ltd., Nasik. The light grey fly ash under the product name "Pozzocrete 83" is available in 30 kg bags. The fly ash produced by the company satisfies all the requirements of the IS: 3812-1981.

### 2.7 Super plasticizer

Polycarboxylate ether base Muraplast FK 30 super plasticizer obtained from MC-Bauchemie (India) Pvt. Ltd. was used. It conforms to IS: 9103-1999.

### 2.8 Steel Fibres

The main variables used in the study are three different types of steel fibres, i.e. Waved Steel Fibres (WSF), Hook Ended Steel Fibres (HESF) and Flat Steel Fibres (FSF) with different dosages of fibres are used by weight of cementations material.

**Table 2.3: Properties of Steel Fibres used**

Type	Length L (mm)	Diameter d (mm)	Aspect Ratio (L/d)
WSF	25	0.55	45
FSF	30	2 mm thick	15
HESF	25	0.55	45

### 2.9 Water

Fresh portable water which is free from concentration of acid and organic substances is used for mixing the concrete and curing.

## III. MIXTURE PROPORTION AND SPECIMEN PREPARATION

The experimental investigation was carried out to study the properties of high strength concrete of M70 grade which was design by DoE method. Silica fume was added as 2.5 % weight of cementitious material and fly is by 10 % weight of cementitious material. There are three types of steel fibres are used in this investigation, i.e. Waved Steel Fibres (WSF), Hook Ended Steel Fibres (HESF) and Flat Steel Fibres (FSF) with different dosages of fibres are used by 0.5 %, 1%, 1.5%, 2%, 2.5%, 3%, 3.5% and 4% weight of cementations material. Table 3.1 shows the mixtures used and their compositional contents.

**Table 3.1: Mix Proportion**

Sr. No	Material	Mass
1	Cementitious Material	556 Kg/m <sup>3</sup>
2	Ordinary Portland Cement (85 % of CM)	472.6 Kg/m <sup>3</sup>
3	Silica fume (2.5 % of CM)	13.75 Kg/m <sup>3</sup>
4	Metakaolin (2.5 %)	13.75 Kg/m <sup>3</sup>
5	Fly Ash (10 % of CM)	55.6 Kg/m <sup>3</sup>
6	Fine Aggregate	702 Kg/m <sup>3</sup>
7	Coarse Aggregate	1042 Kg/m <sup>3</sup>
8	Water	162 Kg/m <sup>3</sup>
9	Superplasticizer	18 ml per kg of Cement
10	Water Binder Ratio	0.29

## IV. METHODOLOGY

### 2.10 Flexural Strength

For flexural strength test, beam specimens of dimensions (100 mm x 100 mm x 500 mm) were cast. The specimens were demoulded after 24 hours of casting and were transferred to curing tank for 28 days. The flexural strength of concrete was determined in accordance with Indian Standards IS: 516-1959. The result obtained are shown in Table 4.1

**Table 4.1: Flexural Strength at 28 Days**

Sr. No	Fibres Volume Fraction Vf (%)	Flexural Strength At 28 Days (MPa)		
		WSF	FSF	HESF
1	0	5.90	5.90	5.90
2	0.5	6.20	6.05	6.04
3	1.0	6.30	6.15	6.10
4	1.5	6.40	6.25	6.15
5	2.0	6.45	6.30	6.20
6	2.5	6.48	6.35	6.25
7	3.0	6.55	6.40	6.30
8	3.5	6.6	6.45	6.35
9	4.0	6.50	6.35	6.25

## V. RESULT AND DISCUSSION

### 2.11 Effect of fibres content (%) on Flexural Strength of Self Compacting High Strength Concrete

The flexural strength increases significantly due to the addition of steel fibres compared with normal concrete. In general, the flexural strength of the concrete having Waving Steel Fibres (WSF) was higher than that of concrete with Flat Steel Fibres (FSF) and Hook Ended Steel Fibres (HESF) at the

same volume fractions of steel up to the limit. The compressive strength of concrete with steel fibres is increased up to the 3.5 % of fibres volume fraction and then decreases. The maximum values of flexural strength at 3.5 % fibres volume fraction are 6.5 MPa, 6.35 MPa and 6.25 MPa for WSF, FSF and HESF respectively. The effect of Silica fume, metakaolin, fly ash and steel fibres on flexural strength of concrete shown in figure 5.1

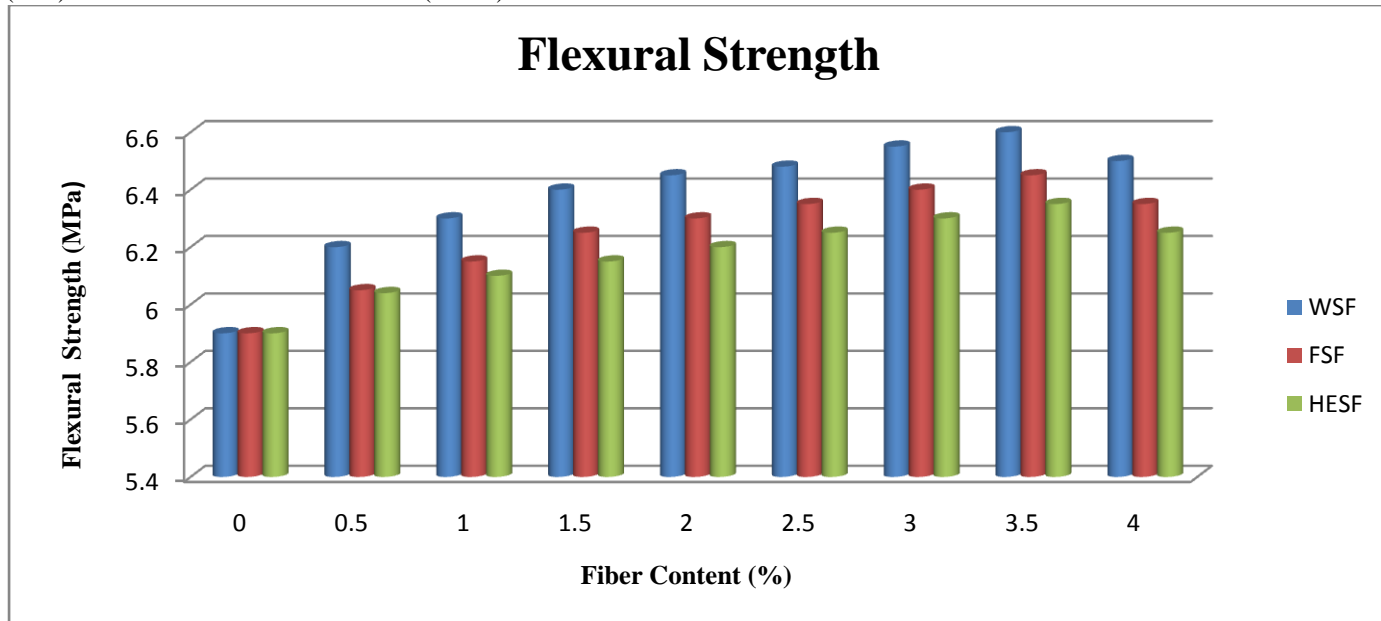


Fig. 5.1 Flexural Strength of concrete with percentage variation of Steel Fibres

## VI. Conclusion

Following conclusions are drawn based on the result discussed above:

1. In general, the significant improvement in flexural strengths is observed with the inclusion of steel fibres in the plain concrete.
2. In general the flexural strength increase with increase in the percentage of fiber content up to certain limit.
3. The optimum fiber content for increase in flexural strength is 3.5%.
4. The flexural strength of concrete increasing with fibres content. The maximum value of flexural strength gives the WSF at 3.5 % fibres content.

## REFERENCES

- [1] Hajime Okamura and Masahiro Ouchi, "Self Compacting Concrete", Journal of Advanced Concrete Technology Vol. 1, No. 1, April 2003, pp. 5-15.
- [2] Khayat K. H., "Workability, Testing and Performance of Self Consolidating Concrete", ACI Materials Journal, Vol. 96, No. 3, May-June 1999, pp.346-354.
- [3] EFNARC, "The European Guidelines for Self Compacting Concrete Specification, Production and Use", May 2005.
- [4] Jacek K., "Steel Fiber and Steel Fiber Reinforced Concrete in Civil Engineering", The Pacific Journal of Science And Technology, Vol. 7, No. 1, May2006, pp.53-58.
- [5] Chuan Mein Wong, "Use of Short Fibres in Structural Concrete to Enhance Mechanical Properties", University of Southern Queensland, November 2004.
- [6] Rame G. M., Narasimhan M.C., Karisddappa and Rajeeva S. V., "Study of the Properties of SCC with Quarry Dust", The Indian Concrete Journal published by ACC limited, Vol.83, No.8, August 2009, pp.54-60.
- [7] Joaquim A.O.B., Lucio A.P., Varma R.K. and Delfina M.F., "Cost Competitive Steel Fiber Reinforced SCC for Structural Applications", The Indian Concrete Journal published by ACC limited, Vol.83, No.8, August 2009, pp.15-26.
- [8] IS: 456-2000, "Indian Standard for code of practice for plain and reinforced concrete".
- [9] IS: 383-1970. "Specification for coarse and Fine Aggregates from natural sources for concrete." Bureau of Indian standards, New Delhi.
- [10] IS: 516-1959, Edition 1.2 (1991-07), "Indian Standard for Methods of test for strength of concrete.
- [11] Sadr Momtazi A, Ranjbar M. M., Balalaei F, Nemati R, "The effect of Iran's Silica fume in enhancing the concrete compressive strength", *Cement and Concrete Research*, pp.-1-7