

“Evaluation of Corrosion Properties of Retrogression and Reaged Al 7075 alloy reinforced with SiC_p Composite Material”

Janardhana. K, Dr. D. N. Drakshayani.

Assistant Professor,

Department of Mechanical Engineering, Sir M.VIT, Bangalore-562157

Professor, Department of Mechanical Engineering, Sir M.VIT, Bangalore-562157.

Abstract:

The metal matrix composites offer a spectrum of advantages that are important for their selection and use as structural materials. A few such advantages are high strength, high elastic modulus, high toughness and impact resistance, low sensitivity to changes in temperature or thermal shock, high surface durability, low sensitivity to surface flaws, high electrical and thermal conductivity, minimum exposure to the potential problem of moisture absorption resulting in environmental degradation and improved machinability with conventional metal working equipment. The aim of the present study is to investigate the corrosion properties of Silicon Carbide particles (SiC_p) reinforced Aluminum matrix composite after retrogression and re-aging heat treatment. Aluminum 7075 alloy with 0%, 5%, 10% and 15% SiC_p were studied.

Key words: Retrogression and Re-aging, Corrosion, Aluminum 7075 alloy, heat treatment.

I. Introduction

Particulate reinforced aluminum alloy matrix composites have received attention over many years due to their excellent yield and tensile strengths, high specific elastic modulus and isotropic properties compared with the conventional alloy materials, which is very good candidate for structural applications in the field of aerospace, automotive and electronics.

The renewed interest in metal matrix composites has been aided by development of reinforcement material which provides either improved properties or reduced cost when compared with existing monolithic materials. [1-2]

Particulate reinforced metal-matrix composites have attracted considerable attention on account of the following aspects: 1. Availability of a spectrum of reinforcements at competitive costs. 2. Successful development of manufacturing processes to produce metal matrix composites with reproducible microstructures and properties. 3. Availability of standard and near standard metal working methods which can be utilized to produce these materials.

7XXX series aluminum alloys are lightweight materials that are widely used in the aerospace industry because of their superior specific strength. The main strengthening mechanism for these alloys is artificial aging commonly known as T6 temper. Although T6 tempered 7XXX series alloys are satisfactorily used in many engineering applications, they suffer from stress corrosion cracking, especially when working in environments containing chloride. Another aging route known as T73 [3] temper has been developed to overcome the drawback. However, T73 temper is accompanied by a loss in

strength of about 10-15%. In 1974, Cina [3] proposed new aging process known as retrogression and reaging to improve the Stress Corrosion Cracking (SCC) resistance of 7075 alloy without significance loss in strength when compared to the T6 temper state.

RRA is applied to T6 tempered 7XXX series alloys into 2 successive steps, namely, retrogression and reaging. [3-6,20]. Taguchi technique is used for design of experiments. The L18 array for each weight percentage of SiC(p) has been chosen and the factors for each specimen will be varied as required.

II. Experimentation:

The nominal composition of Al-7075 alloy is given in Table 1.

Elements	Wt (%)
Cu	1.2 - 2
Mg	2.1 - 2.9
Zn	5.1 - 6.1
Cr	0.18-0.28
Si	<0.4
Al	87.1-97.4
Fe	<0.5

Table 1: Composition of Al-7075

Stir casting method is used to obtain the Al 7075/SiC p composite. Aluminum 7075 was introduced

into the furnace at 660 °C, so as to obtain its liquid phase. After obtaining a melt, silicon carbide powder pre heated at 300°C for 30 minutes was added to it. Mechanical agitation was done to get a homogenous melt. This mixture is then casted into fingers of specific dimensions. Preaging is carried out at temperatures of 125°C, 135°C and 145°C for time periods of 12, 24 and 48 hs. Then Retrogression is carried out at temperatures of 200°C, 220°C and 240°C for 5, 10 and 15 mins followed by reaging at 125°C, 135°C and 145°C for 12 , 24 and 48 hs.. The heat treatment is carried out in a Muffle Furnace. These heat treated specimens are then immersed in 5% & 10% NaCl (by weight) solution for 12, 24 and 48 hs. The specimens were machined to the required dimensions (Fig. 3.) for the tensile test. The results are plotted in L18 arrays and Statistical Analysis Software MINITAB 16 by Taguchi method is used for analysis.

2.1.1. Stir Casting

Casting Process was carried out to prepare the samples as discussed in earlier paper. [20] All specimens were then coded as indicated in section 2.2.



Fig 1. Furnace with stirring apparatus

2.1.2. Heat Treatment

- Retrogression and reaging treatment can improve the stress corrosion behavior of the alloy while maintaining the mechanical resistance of the T6 temper [4-12, 20-21].



Fig 2. Heat treatment in muffle furnace

2.1.3. Corrosion

- 5% & 10% NaCl solution (by weight) or 1M and 2 M was prepared using distilled water.
- The heat treated specimens were immersed in the solution taken in glass jar for 12, 24 & 48 hours for respective trials.
- The weight of the specimens before and after corrosion was noted down.

2.2. Methodology

Experimental design using Taguchi method.

Eight factors and(one factor at 2 level and seven factors at 3 levels) levels for parameters have been chosen for each specimen composition as given in Table 2.

The L18 array for each weight % fraction of SiC has been chosen and the coding of the specimen is done as follows.

Percentage of SiC,%	A - 0	B -10	C - 20
Preage temperature, °C	1 - 125	2 - 135	3 - 145
Preage time, hs	A - 12	B - 24	C - 48
Retrogression temperature, °C	1 - 200	2 - 220	3 - 240
Retrogression time, hs	A - 5	B - 10	C - 15
Reage temperature, °C	1 - 125	2 - 135	3 - 145
Reage time, hs	A - 12	B - 24	C - 48
%NaCl (wt)	A-5	B- 10	
Soaking time ,hs	A-12	B- 24	C - 48

Table 2: Eight factors and levels for each parameter.

If a specimen is labeled A2B3C1AAB, then the specimen condition is as indicated below:

1. 0% SiC
2. Pre-aged at 135 °C
3. For 24 hs
4. Retrogressed at 240 °C
5. For 15 minutes
6. Re-aged at 125 °C
7. For 12 hs
8. Immersed in 5% NaCl
9. For 24hs

2.3. Tensile Test

It was carried out as per ASTM standards E8- 95A. All the samples were tested for strength.

The samples were loaded till fracture.

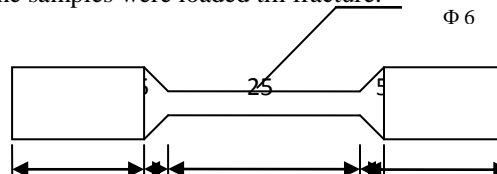


Fig 3: Tensile test specimen

III. Results and Discussion

3.1. Taguchi Method

Taguchi technique using Minitab 16 Statistical Software was applied to analyze the L18 array for each of the specimens. Totally 4 arrays were used. In each 4 different percentages (0%, 10%, 15% and 20%) of SiC were considered. Main effects Graphs for means and S/N ratios were obtained showing relationships between the output result and the various factors.

For Tensile strength, the larger the better condition is selected.

3.2. Tensile strength

3.2.1. REGRESSION EQUATIONS (0% SiC):

$$\text{TENSILE STRENGTH} = - 4 - 0.81 \% \text{NaCl} - 1.24 \text{ PREAGE TEMP} + 0.380 \text{ PREAGE TIME} - 0.238 \text{ RETRO TEMP} + 1.83 \text{ RETRO TIME} + 2.12 \text{ REAGE TEMP} - 0.026 \text{ REAGE TIME} + 0.443 \text{ SOAKING TIME} \dots\dots\dots 1$$

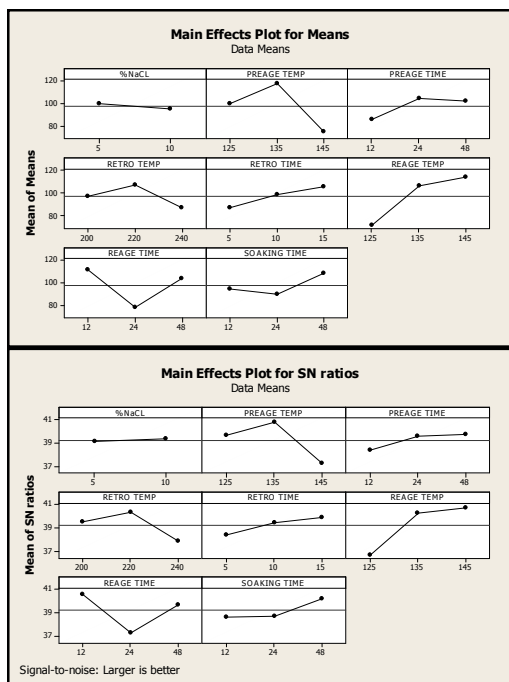


Fig. 4: Main effects plot for Means and S/N ratios of 0% SiC

From Fig.4 it is observed that, the specimens which are preaged at 135°C for 48 hs, retrogressed at 220°C for 15 minutes, reaged at 145°C for 12hs and immersed in 10% NaCl for 48hs shows the improved tensile strength of the composite material. Also, the specimens which are preaged at 145°C for 12 hs, retrogressed at 240°C for 5 minutes, reaged at 125°C for 24 hs and immersed in 5% NaCl for 12hs exhibited the poorer tensile strength. The increase in the strength of the specimens are due to the formation of the more stable interphases like MgZn₂

[12-14] and also refinement of the grains at the said elevated temperature of retrogression for short interval of time. Whereas the specimens which are subjected to lower retrogressed temperature for short interval of time and higher reaging temperature for longer reaging time resulting in the coarsening of the interphases and formation of more unstable precipitates.

3.2.2. REGRESSION EQUATIONS (5% SiC):

$$\text{TENSILE STRENGTH} = - 21 + 0.82 \% \text{NaCl} + 1.42 \text{ PREAGE TEMP} + 0.296 \text{ PREAGE TIME} + 0.554 \text{ RETRO TEMP} - 1.47 \text{ RETRO TIME} - 1.35 \text{ REAGE TEMP} + 1.43 \text{ REAGE TIME} - 0.654 \text{ SOAKING TIME} \dots\dots\dots 2$$

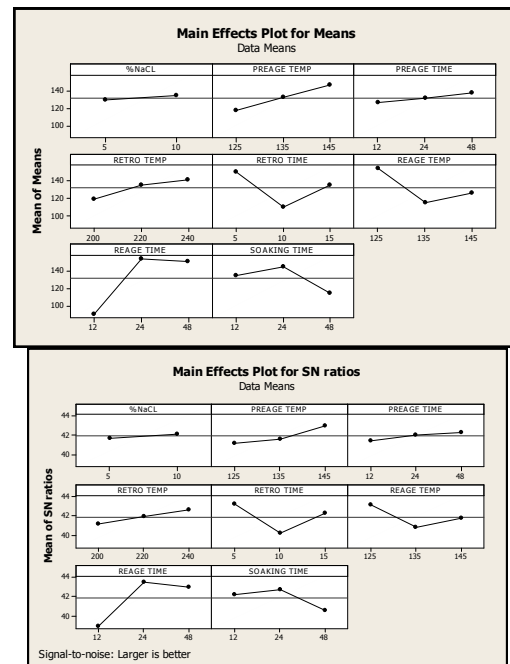


Fig. 5: Main effects plot for Means and S/N ratios of 5% SiC

From Fig.5 its observed that, the specimens which are preaged at 145°C for 48 hs, retrogressed at 240°C for 5 minutes, reaged at 125°C for 24 hs and immersed in 10% NaCl for 24hs improved the tensile strength of the composite material. Also, the specimens which are preaged at 125°C for 12 hs, retrogressed at 200°C for 10 minutes, reaged at 135°C for 12 hs and immersed in 5% NaCl for 48hs exhibits poor tensile strength.

3.2.3. REGRESSION EQUATIONS (10% SiC):

$$\text{TENSILE STRENGTH} = - 33 + 2.32 \% \text{NaCl} + 1.46 \text{ PREAGE TEMP} - 0.174 \text{ PREAGE TIME} + 0.505 \text{ RETRO TEMP} + 0.02 \text{ RETRO TIME} - 1.49 \text{ REAGE TEMP} + 0.544 \text{ REAGE TIME} - 0.198 \text{ SOAKING TIME} \dots\dots\dots 3$$

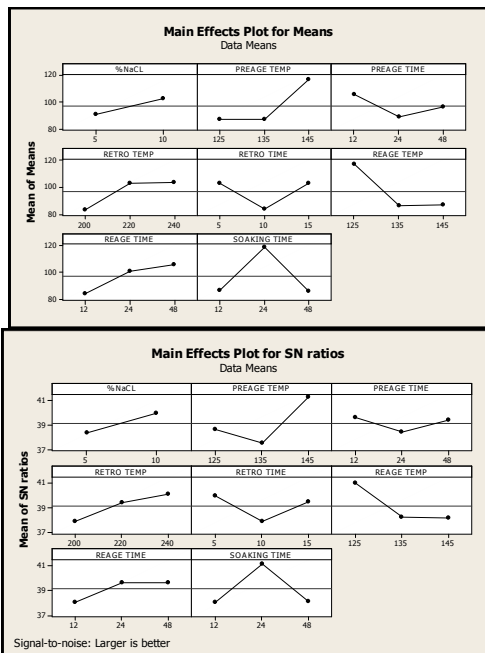


Fig. 6: Main effects plot for Means and S/N ratios of 10% SiC

3.2.4. REGRESSION EQUATIONS (15% SiC):

$$\text{Tensile strength} = -696.705 + 3.458 \% \text{NaCl} + 0.7268 \text{ PREAGE TEMP} + 0.394167 \text{ PREAGE TIME} + 3.3538 \text{ REAGE TEMP} + 1.56467 \text{ REAGE TIME} + 1.0865 \text{ RETRO TEMP}$$

4

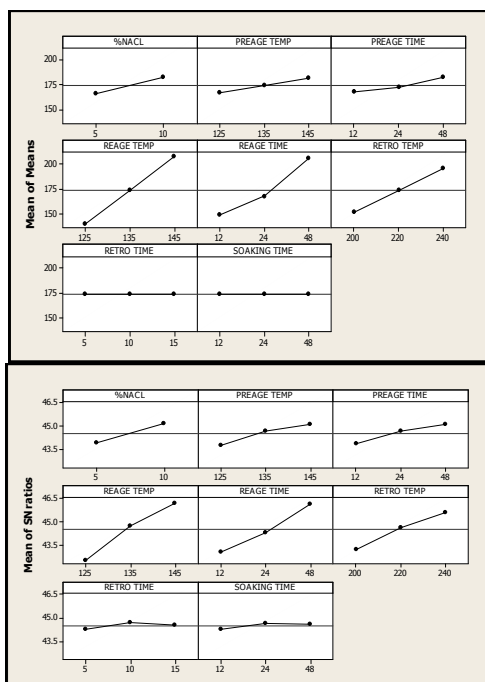


Fig. 7: Main effects plot for Means and S/N ratios of 15% SiC

From Equation 1, 2, 3 and 4 it's observed that the relationship between the stated parameters is

established and also able to estimate the tensile strength for the different values of the parameters.

From Fig.6 its observed that, the specimens which are preaged at 145°C for 12 hs, retrogressed at 240°C for 5 minutes and reaged at 125°C for 24 and immersed in 10% NaCl for 24hs improved the tensile strength of the composite material. Also, the specimens which are preaged at 135°C for 24 hs, retrogressed at 200°C for 10 minutes, reaged at 125°C for 12 hs and immersed in 5% NaCl for 12hs exhibits poor tensile strength.

From Fig.7 its observed that, the specimens which are preaged at 145°C for 48hs, retrogressed at 240°C for 10 minutes, reaged at 145°C for 48 hs and immersed in 10% NaCl for 24hs improved the tensile strength of the composite material. Also, the specimens which are preaged at 125°C for 12 hs, retrogressed at 200°C for 5 minutes, reaged at 125°C for 12 hs and immersed in 5% NaCl for 12hs exhibit poor tensile strength.

IV. Conclusions

From the present studies, the following conclusions were obtained.

1. With increase in temperature and time of all the three phases of RRA, pre-aging, retrogression and reaging, the Tensile Strength increases generally.
2. At higher pre-aging and re-aging temperatures, increase in Tensile Strength can be due to the relieving of internal stresses within the material and refinement of the grains.
3. The effect of higher % of Nacl and longer soaking time on the composite material subjected to higher retrogression temperature for short duration is minimal.

V. Acknowledgement

The authors sincerely thank the Management and Staff of Department of Mechanical Engineering, Sir M.VIT and Family members.

References

- [1.] R.J.Bucci, C.J.Warren, E.A.Starke,Jr. "The need for new aging aircraft structures".
- [2.] S.Das, "Development of aluminium alloy composites for engineering applications". Trans.Indian Inst. Met. Vol.57, No.4, Pp.325-334, August 2004.
- [3.] Baruch M.Cina, "Reducing the susceptibility of alloys, particularly alluminium alloys,to Stress corrosion cracking", United states Patent [19], [11] Patent no: 3, 856, 584, [45] Date Of Patent: Dec.24, 1974.
- [4.] Bruno Dubost; Jean Bouvaist, "Process for thermal treatment of thin 7000 series alluminium alloys and products obtained", United States Patent [19], [11] Patent no:

- 4,189,334, [45] Date Of Patent: Feb.19, 1980.
- [5.] Melvin H. Brown, "Three-step aging to obtain high strength and corrosion resistance in Al-Zn-Mg-Cu alloys". United States patent [19], [11] Patent no: 4,477,292, [45] Date Of Patent: Oct.16.1984.
- [6.] Melvin H. Brown, "Producing combined high strength and high corrosion resistance in Al-Zn-Mg-Cu alloys". United States patent [19], [11] Patent no: 4,832,758, [45] Date Of Patent: May.23.1989.
- [7.] Manabu.Nakai; Takehiko Eto, "High strength heat treatable 7000 series aluminium alloy of excellent corrosion resistance and a method of Producing thereof" United States patent [19], [11] Patent no: 6,048,415, [45] Date Of Patent: Apr.11.2000.
- [8.] W.Zhou , Z.M.Xu, "Casting of SiC reinforced Metal Matrix Composites", *Journal of Materials Processing Technology* , Vol. 63, Pg. 358- 363, 1997.
- [9.] D.Peeler,D.Raizenne,P.Sjoblom,R.Rondeau, S.Kulhman,J.Snide, "Retrosession and re-aging (RRA)of aluminium 7075-T56 aircraft Components".
- [10.] F.Viana, A.M.P.Pinto, H.M.C Santos, A.B Lopes, "Retrosession and Re-ageing of 7075 Aluminium Alloy: Micro structural Characterization". *Journal of materials processing technology*, 92-93, Pg 54-59, 1999.
- [11.] Marko Tandler, Borivoj Sustarsic, Leopold Vehovar,Matjaz Torkar, "Corrosion of Al/SiC metal- matrix composites" ISSN 1580- 2949, MATRE. TEHNOL. Vol.34, No. (6), 2000.
- [12.] Andrzej Zieinski, Malgorzata Warmuzek, Andrzej Gazda, Elzbieta Jezierska, Jarek Chrzanowski, "Influence of Retrosession and Reaging (RRA) heat treatment on Microstructure, Mechanical and Chemical behaviour of an Al-Zn-Mg Alloy", *Advances in Material Science*, Vol.2, No.1 (2), 33-42, 2002.
- [13.] Es-Said. O.S.,Frazier.W.E, Lee E.W, " The effect of Retrosession and Reaging on the properties of the 7249 Aluminium alloys", *JOM*,2003.
- [14.] A.Grosvenor,C.H.J.Davies,K.Sharp, "The effect of retrosession and reaging treatment on residual stress in AA7075" *Materials Forum* Volume 28-Published 2004.
- [15.] FENG Chun, Liu Zhi-yi, NING ai-lin, LIU yan-bin, ZENG Su-min, "Retrosession and re-aging treatment of Al-9099%Zn-1.72%Cu- 2.5%Mg-0.13%Zr Aluminium alloy" *Transactions of Nonferrous Metals Society Of China*, Vol. 16 , Pg. 1163-1170, 2006.
- [16.] FENG Chun,LiuZhi-yi, NING ai-lin, LIU yan-bin, ZENG Su-min, "Effect of low temperature aging on microstructure and mechanical Properties of super high strength aluminium alloy". Article ID: 1005-9784(2006)05-0461-07.
- [17.] RanjitBauri, M.K.Surappa, "Processing and properties of Al-Li-SiC_(p)Composites", *Science and Technology of Advanced Materials*, Vol. 8, pg 494-502, 2007.
- [18.] K.S.Ghosh, K.Das, U.K.Chatterj, "Environmental induced cracking in Al-Li-Cu-Mg-Zr alloys of peak aged and retrosession and reaged Tempers under applied potentials" *TMS (The Minerals, Metals &Materials Society)*, 2007.
- [19.] Sun yun-ping,YAn Hong-ge,Chen Zhen-hua,Zhang Hao, "Effect of heat-treatment on microstructure and properties of SiC particulate-reinforced Aluminium matrix composite", *Transactions Of Nonferrous Metals Society Of China* ,Vol.17, pg 318-321, 2007.
- [20.] Janardhana K, Dr.D N Drakshayani, "Evaluation of Mechanical Properties of Retrosession and Reaged Al 7075 alloy reinforced with SiCp Composite Material", *IJERT*, Volume. 3, Issue. 09, 406-409, September – 2014.
- [21.] Janardhana K, Dr.D N Drakshayani, "Evaluation of Mechanical Properties of Retrosession and Reaged Al 7075 alloy reinforced with SiCp Composite Material", *IJRET*, Volume: 03 Issue: 11, Nov-2014.