

## Valuation of surfactant Phosphonates synthesized in the protection of metal surfaces against corrosion of mild steel in 0.5M H<sub>2</sub>SO<sub>4</sub> media

R. Ghibate<sup>1\*</sup>, F. Sabry<sup>1\*\*</sup>, Y. Kharbach<sup>2</sup>, Y. Kandri Rodi<sup>2</sup>, M.K. Skalli<sup>2</sup>, A. Haoudi<sup>2</sup>, O. Senhaji<sup>1</sup>, M. Touzani<sup>1</sup>, R. Taouil<sup>1</sup>, A. Aouniti<sup>3</sup>, B. Hammouti<sup>3</sup>

<sup>1</sup>Laboratory of Applied Physical Chemistry, Faculty of Science and Technology, University My. Ismail, Errachidia, Morocco.

<sup>2</sup>Laboratory of Applied Chemistry, Faculty of Science and Technology, University S. M. Benabdellah, Fes, Morocco.

<sup>3</sup>Laboratory of Applied Chemistry & Environment, Faculty of Science, University Mohamed V, Oujda, Morocco.

E-mails: \* [rajae.ghibate@gmail.com](mailto:rajae.ghibate@gmail.com), \*\* [fatima.sabry89@gmail.com](mailto:fatima.sabry89@gmail.com)

### ABSTRACT

In this article, we are interesting to investigate the corrosion inhibition of mild steel in sulfuric acid by two surfactants phosphonates already synthesized namely sodium methyl dodecyl phosphonate (Pho1) and sodium methyl (11-methacryloyloxyundecyl) phosphonate (Pho2).

The inhibition performances of Pho1 and Pho2 on mild steel corrosion in 0.5M H<sub>2</sub>SO<sub>4</sub> solution were studied using the electrochemical impedance spectroscopy (EIS), weight loss, and Tafel polarization techniques. The experimental results suggest that those surfactants are effective corrosion inhibitors and the inhibition efficiency increases with the increase surfactants concentrations. Polarization measurements proved that the inhibitors behave as mixed-type. EIS diagram appears a large capacitive loop at high frequencies (HF) followed by a small inductive loop at low frequencies (LF) for Pho2, and the addition of this surfactant inhibitor increases the impedance of electrode. The adsorption of each surfactant on steel surface obeys Langmuir adsorption isotherm. The thermodynamic and kinetic parameters were calculated and discussed. Values of inhibition efficiency calculated from weight loss, Tafel polarization curves, and EIS are in good agreement.

**Keywords**-Surfactant phosphonates, mild steel, corrosion inhibition, H<sub>2</sub>SO<sub>4</sub> acid, weight loss, polarization, EIS

### I. INTRODUCTION


Acid solutions are widely used in industry. The corrosion of steel in acidic solution receives considerable concern. Sulfuric acid is one of the most aggressive acids for iron and its alloys and is often used during cleaning, pickling, descaling, acidizing, we use corrosion inhibitors to reduce the corrosion rates of metallic materials in acidic media [1-3].

The use of corrosion inhibitors is one of the most practical methods for protection of steel against corrosion in acidic solutions. Most of well-known acid corrosion inhibitors are organic compounds containing nitrogen, sulfur or oxygen atoms [4-6]. Those organic inhibitors molecules apply their inhibition action via the adsorption of the inhibitor molecules onto the metal/solution interface [7-9]. The adsorption process is affected by the chemical structures of the inhibitors, the nature and charged surface of the metal and the distribution of charge over the whole inhibitor molecule.

The phosphonate derivatives have been successfully used as corrosion inhibitors in many practical applications [10-12], and they are effective

corrosion inhibitors for aluminum, copper and steel in hydrochloric, nitric and sulfuric acid solutions [13-18]. The encouraging results obtained by these compounds have incited us to test their effect on the corrosion behaviour of mild steel in sulfuric acidic media (0.5M H<sub>2</sub>SO<sub>4</sub>).

In this article, we are interesting to investigate the corrosion inhibition of mild steel in sulfuric acid by two already synthesized phosphonate derivatives [19,20] (scheme 1) namely sodium methyl dodecyl phosphonate (Pho1) and sodium methyl (11-methacryloyloxyundecyl) phosphonate (Pho2). The chemical structures of those compounds are given in scheme 1. The corrosion inhibitive activity of those organic compounds was examined successively via weight loss, potentiodynamic polarization curves, electrochemical impedance spectroscopy (EIS). The kinetic and adsorption parameters of corrosion inhibition process are also evaluated.

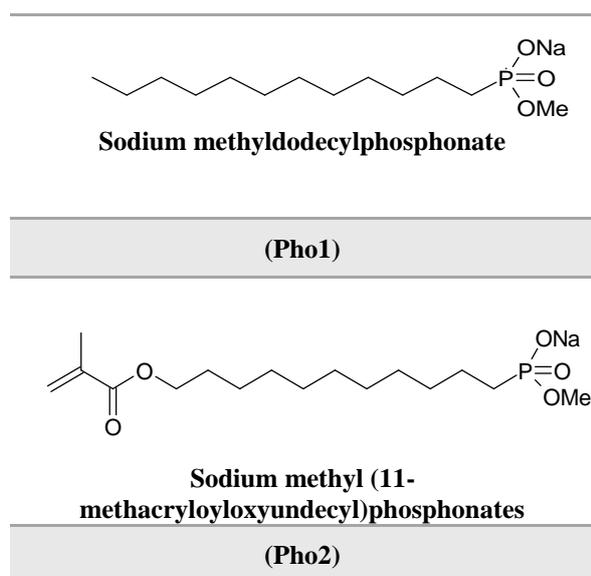

**Scheme 1.** Chemical formulas of Pho1 and Pho2.

## II. EXPERIMENTAL SECTION

### 2.1. Materials

The steel used in this study is a mild steel with a chemical composition (in wt%) of 0.09%P, 0.01 % Al, 0.38 % Si, 0.05 % Mn, 0.21 % C, 0.05 % S and the remainder iron (Fe). The steel samples were pre-treated prior to the experiments by grinding with amery paper SiC (220, 400, 800, 1000 and 1200); rinsed with distilled water, degreased in acetone, washed again with bidistilled water and then dried at room temperature before use.

### 2.2. Solutions

The aggressive solutions of 0,5M H<sub>2</sub>SO<sub>4</sub> were prepared by dilution of analytical grade 97% H<sub>2</sub>SO<sub>4</sub> with distilled water. The concentration range of sodium methyl dodecylphosphonate (Pho1) and sodium methyl (11-methacryloyloxyundecyl) phosphonate (Pho2) used was 10<sup>-6</sup>M to 10<sup>-3</sup>M.

### 2.3. Gravimetric study

Gravimetric experiments were performed according to the standard methods; the mild steel sheets of 1.5 cm × 1.5 cm × 0.03 cm were abraded with a series of emery papers sic (220, 400, 800, 1000 and 1200) and then washed with distilled water and acetone. After weighing accurately, the specimens were immersed in a 50 mL beaker containing 100 mL of 0,5M H<sub>2</sub>SO<sub>4</sub> solution with and without addition of different concentrations inhibitor. All the aggressive acid solutions were open to air. After 6 h of acid immersion, the specimens were taken out, washed, dried, and weighed accurately. In order to get good reproducibility, all measurements were performed few times and average values were reported to obtain good reproducibility. The

inhibition efficiency ( $\eta_{WL}\%$ ) and surface coverage ( $\theta$ ) were calculated as follows:

$$C_R = \frac{W_b - W_a}{At} \quad (1)$$

$$\eta_{WL}(\%) = \left(1 - \frac{w_i}{w_0}\right) \times 100 \quad (2)$$

$$\theta = \left(1 - \frac{w_i}{w_0}\right) \quad (3)$$

where  $W_b$  and  $W_a$  are the specimen weight before and after immersion in the tested solution,  $w_0$  and  $w_i$  are the values of corrosion weight losses of mild steel in uninhibited and inhibited solutions, respectively,  $A$  the total area of the mild steel specimen (cm<sup>2</sup>) and  $t$  is the exposure time (h).

### 2.4. Electrochemical measurements

The electrochemical measurements were carried out using Volta lab (Tacussel- Radiometer PGZ 100) potentiostat and controlled by Tacussel corrosion analysis software model (Voltmaster 4) at under static condition. The corrosion cell used had three electrodes. The reference electrode was a saturated calomel electrode (SCE). A platinum electrode was used as auxiliary electrode of surface area of 1 cm<sup>2</sup>. The working electrode was mild steel of the surface 0.04 cm<sup>2</sup>. All potentials given in this study were referred to this reference electrode. The working electrode was immersed in test solution for 30 min to a establish steady state open circuit potential ( $E_{ocp}$ ).

After measuring the  $E_{ocp}$ , the electrochemical measurements were performed. All electrochemical tests have been performed in aerated solutions at 308 K. The EIS experiments were conducted in the frequency range with high limit of 100 kHz and different low limit 0.1 Hz at open circuit potential, with 10 points per decade, at the rest potential, after 30 min of acid immersion, by applying 10 mV ac voltage peak-to-peak. Nyquist plots were made from these experiments. The best semicircle can be fit through the data points in the Nyquist plot using a non-linear least square fit so as to give the intersections with the  $x$ -axis.

After ac impedance test, the potentiodynamic polarization measurements of mild steel substrate in inhibited and uninhibited solution were scanned from cathodic to the anodic direction, with a scan rate of 1 mV s<sup>-1</sup>. The potentiodynamic data were analysed using the polarization VoltaMaster 4 software. The linear Tafel segments of anodic and cathodic curves were extrapolated to corrosion potential to obtain corrosion current densities ( $I_{corr}$ ).

## III. RESULTS AND DISCUSSION

### 3.1. Polarization Measurements

Potentiodynamic polarization data of various concentrations of Pho1 and Pho2 are shown as the Tafel plots steel in 0,5M H<sub>2</sub>SO<sub>4</sub> in Figures 1 and 2. The corrosion kinetic parameters such as corrosion potential (E<sub>corr</sub>), corrosion current density (I<sub>corr</sub>), cathodic Tafel slopes (β<sub>c</sub>) were derived from these curves and are given in Table1.

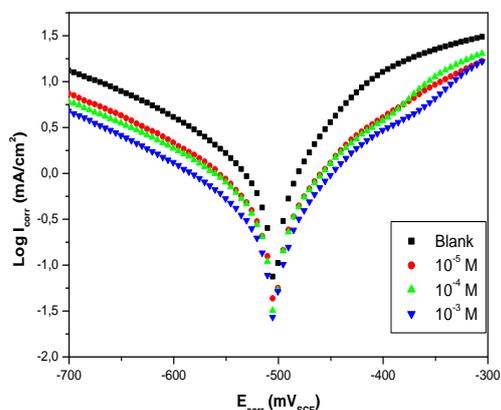


Figure1. Polarization curves of steel in 0.5M H<sub>2</sub>SO<sub>4</sub> containing various concentrations of Pho1.

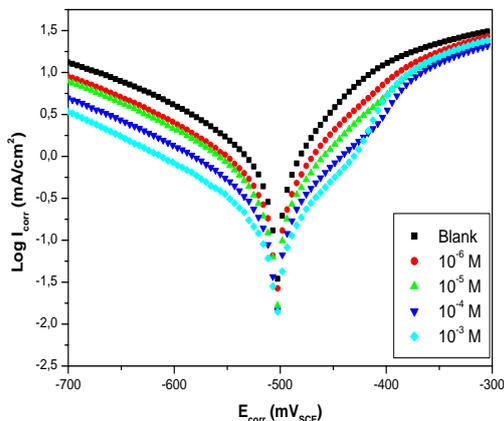


Figure 2. Polarization curves of steel in 0.5M H<sub>2</sub>SO<sub>4</sub> containing various concentrations of Pho2.

The values of inhibition efficiency (E<sub>1</sub>%) were calculated using the following equation:

$$E_1 \% = \frac{I_{corr} - I_{corr(inh)}}{I_{corr}} \times 100 \quad (4)$$

Where I<sub>corr</sub> and I<sub>corr(inh)</sub> are the values of corrosion current densities of steel without and with the additive, respectively, which were determined by extrapolation of the cathodic Tafel lines to the corrosion potential E<sub>corr</sub>.

Table 1. Electrochemical data of steel at various concentrations of Pho1 and Pho2 in 0.5M H<sub>2</sub>SO<sub>4</sub> and corresponding inhibition efficiencies.

	Conc n (M)	-E <sub>corr</sub> (mV/SC E)	β <sub>c</sub> (mV/de e)	I <sub>corr</sub> (μA/cm <sup>2</sup> )	E <sub>1</sub> (%)
Blank	0.5	534	199	1560	--
Pho1	10 <sup>-6</sup>	535	169	760	51
	10 <sup>-5</sup>	532	171	680	56
	10 <sup>-4</sup>	533	205	510	67
	10 <sup>-3</sup>	539	172	380	76
Pho2	10 <sup>-6</sup>	529	168	730	53
	10 <sup>-5</sup>	530	181	630	60
	10 <sup>-4</sup>	528	159	340	78
	10 <sup>-3</sup>	521	169	210	87

The data in Table 1 indicate that in both cases I<sub>corr</sub> values gradually decreased with the increase of the inhibitor concentration with respect to the blank. Inhibition efficiency (E<sub>1</sub>) at 10<sup>-3</sup> M reaches up to a maximum of 86% for Pho2; and 75% for Pho1, which again confirms that both inhibitors are good inhibitors for steel in 0,5M H<sub>2</sub>SO<sub>4</sub>, and E<sub>1</sub> follows the order: Pho2 > Pho1. According to the literature [21], it has been reported that (i) if the shift in E<sub>corr</sub> is < 85 mV the inhibitor can be claimed as mixed type and (ii) if the shift in E<sub>corr</sub> is > 85 mV, with respect to E<sub>corr</sub>, the inhibitor behave as either cathodic or anodic. In this investigation, the shift in E<sub>corr</sub> is less than 25 mV for Pho2 and is even less for Pho1, suggesting that both Pho2 and Pho1 act as mixed type of inhibitors [22].


### 3.2. Electrochemical Impedance Spectroscopy

The EIS was carried out on a newly polished steel surface in acidic solution in the absence and presence of Pho2 at open circuit potential at 308 K after 30 min of immersion. Nyquist plots of steel in 0,5M H<sub>2</sub>SO<sub>4</sub> in the presence and absence of additive are given in Figure 3. These curves have obtained after 30 min of immersion in the corresponding solution. Impedance parameters derived from the Nyquist plots are given in Table 2. The charge transfer resistance, R<sub>t</sub> values are calculated from the difference in impedance at lower and higher frequencies. To obtain the double layer capacitance (C<sub>dl</sub>), the frequency at which the imaginary component of the impedance is maximum (-Z<sub>max</sub>) is found and C<sub>dl</sub> values are obtained from the equation:

$$f(-Z_{max}) = \frac{1}{2\pi C_{dl} R_t} \quad (5)$$

The figure 3 represents the Nyquist diagrams for mild steel in 0,5M H<sub>2</sub>SO<sub>4</sub> in the presence of Pho2, respectively. Clearly, the impedance spectra exhibit a large capacitive loop at high frequencies followed by a small inductive loop at low frequency values. In the presence of Pho2, comparing with blank solution, the shape is maintained throughout all tested

concentrations, indicating that almost no change in the corrosion mechanism occurs due to the inhibitor addition [23]. The capacitive loop indicates that the corrosion of steel is mainly controlled by a charge transfer process, and usually related to the charge transfer of the corrosion process and double layer behavior. On the other hand, the inductive loop may be attributed to the relaxation process obtained by adsorption species like FeSO<sub>4</sub> [24] or inhibitor species [25] on the electrode surface.

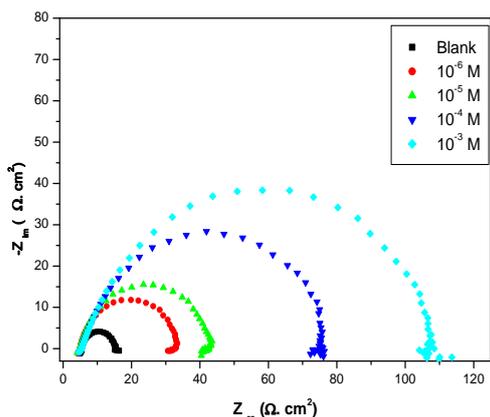

**Figure 3.** Nyquist diagrams for steel in 0.5M H<sub>2</sub>SO<sub>4</sub> containing different concentrations of Pho2.

The diameter of the capacitive loop in the presence of inhibitor is bigger than that in the absence of inhibitor (blank solution) and increases with the inhibitor concentration. This indicates that the impedance of inhibited substrate increases with the inhibitor concentration. Noticeably, these capacitive loops are not perfect semicircles which can be attributed to the frequency dispersion effect as a result of the roughness and inhomogeneous of the electrode surface [26].

**Table 2.** Characteristic parameters evaluated from the impedance diagram for steel in 0.5M H<sub>2</sub>SO<sub>4</sub> at various concentrations of Pho2.

	Conc (M)	R <sub>t</sub> (Ω.cm <sup>2</sup> )	C <sub>dl</sub> (μF/cm <sup>2</sup> )	E (%)
Blank	0.5	10.04	79.2	--
Pho2	10 <sup>-6</sup>	27.4	46.45	63
	10 <sup>-5</sup>	37.17	34.25	72
	10 <sup>-4</sup>	69.34	31.24	85
	10 <sup>-3</sup>	101.8	28.92	90

Data in Table 2 shows that additional Pho2 inhibits the corrosion of mild steel in 0.5 M H<sub>2</sub>SO<sub>4</sub>. The inhibition efficiency is calculated using charge transfer resistance from the equation [15]:

$$E_{Rt} \% = \frac{R_{t\text{corr}}^{-1} - R_{t\text{corr}}^{-1}(\text{inh})}{R_{t\text{corr}}^{-1}} \times 100 \quad (6)$$


Where R<sub>tcorr</sub> and R<sub>tcorr(inh)</sub> are the charge transfer resistance values in absence and presence of inhibition for steel in 0.5M H<sub>2</sub>SO<sub>4</sub>, respectively.

By increasing the inhibitor concentration the R<sub>t</sub> values increase but C<sub>dl</sub> values decrease. According to Helmholtz model, the double layer capacitance C<sub>dl</sub> is given by:

$$C_{dl} = \frac{\epsilon_0 \epsilon}{\delta} S \quad (7)$$

Where δ is the thickness of the deposit, S is the surface of the electrode, ε<sub>0</sub> is the permittivity of the air, and ε is the medium dielectric constant.

As can be seen from this Table 2 and figure 4 the decrease in C<sub>dl</sub>, which can result from a decrease in local dielectric constant and/or an increase in the thickness of the electric double layer [27,28], suggested that Pho2 molecules function by adsorption at the metal/solution interface. Thus, the decrease in C<sub>dl</sub> values and the increase in R<sub>t</sub> values and consequently of inhibition efficiency may be due to the gradual replacement of water molecules by the adsorption of the Pho molecules on the metal surface, decreasing the extent of dissolution reaction [29].

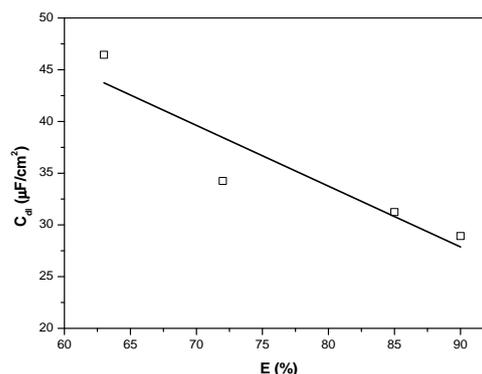

**Figure 4.** Evolution of C<sub>dl</sub> with the inhibition efficiency of Pho2

### 3.3. Weight Loss Tests

#### 3.3.1. Effect of concentration

The table 3 collects the corrosion rates and the inhibition efficiencies evaluated from weight loss measurements for different inhibitor concentrations in 0,5M H<sub>2</sub>SO<sub>4</sub>. The corrosion rate reduces after addition of the selected two compounds, and decreases with the inhibitor concentration. This behaviour is due to the fact that the adsorption coverage increases with the increase of inhibitor concentration, which shields the mild steel surface efficiently from the medium. In the absence of inhibitor, the corrosion rate is as high as 11.679 mg cm<sup>-2</sup> h<sup>-1</sup>. While in the presence of 10<sup>-3</sup> M inhibitor, the corrosion rate values are reduced to 1.353 and 0.891 mg cm<sup>-2</sup> h<sup>-1</sup> for Pho1 and Pho2, respectively. At any given inhibitor concentration, the corrosion rate follows the order: C<sub>R</sub> (Pho2) < C<sub>R</sub> (Pho1), which

indicates that Pho2 exhibits the best inhibitive performance among two compounds.

**Table 3.** Gravimetric results of steel in acid without and with addition of Pho1 and Pho2, 6h at 308K.

Inhibitor	Conc (M)	$C_R$ (mg/cm <sup>2</sup> .h)	$\eta_{wt}$ (%)	$\theta$
Blank	0.5	11.679	--	--
Pho1	10 <sup>-6</sup>	11.284	3	0.03
	10 <sup>-5</sup>	10.717	8	0.08
	5×10 <sup>-5</sup>	10.335	11	0.11
	10 <sup>-4</sup>	7.641	34	0.34
	5×10 <sup>-4</sup>	1.656	85	0.85
	10 <sup>-3</sup>	1.353	88	0.88
Pho2	10 <sup>-6</sup>	10.926	6	0.06
	10 <sup>-5</sup>	10.094	13	0.13
	5×10 <sup>-5</sup>	8.780	24	0.24
	10 <sup>-4</sup>	4.923	57	0.57
	5×10 <sup>-4</sup>	2.089	82	0.82
	10 <sup>-3</sup>	0.891	92	0.92


### 3.3.2. Effect of temperature and thermodynamic activation parameters

Temperature has a great effect on the corrosion phenomenon. Generally the corrosion rate increases with the rise of the temperature. For this purpose, we made weight loss experiments in the range of temperature 313-353 K, in the absence and presence of various concentrations of Pho1 and Pho2 after 1h of immersion. The corresponding data are shown in Table 4, it is clear that the inhibition efficiencies decrease with the increase of temperature.


**Table 4.** Inhibition efficiencies obtained from the corrosion rate 10<sup>-3</sup> M of phosphonates in 0.5M H<sub>2</sub>SO<sub>4</sub> at different temperatures at 1h.

Temp (K)	Inhibitors	$C_R$ (mg/cm <sup>2</sup> .h)	$\eta_{wt}$ (%)	$\theta$
313	Blank	16,241	--	--
	Pho1	0,227	98,6	0,98
	Pho2	0,324	97,9	0,97
323	Blank	30,160	--	--
	Pho1	8,093	73,1	0,73
	Pho2	0,696	97,6	0,97
333	Blank	46,535	--	--
	Pho1	17,637	62,0	0,62
	Pho2	3,117	93,3	0,93
343	Blank	59,750	--	--
	Pho1	35,235	41,0	0,41
	Pho2	14,293	76,0	0,76
353	Blank	85,672	--	--
	Pho1	57,534	32,8	0,32
	Pho2	36,0	57,9	0,57

The figure 5 shows that the corrosion rate increases as temperature rises, and the values of inhibition efficiency of Pho2 is more than Pho1. The results show that the inhibition efficiencies decrease with increasing temperature, indicating that at higher temperature dissolution of steel predominates over inhibitor adsorption at the surface.

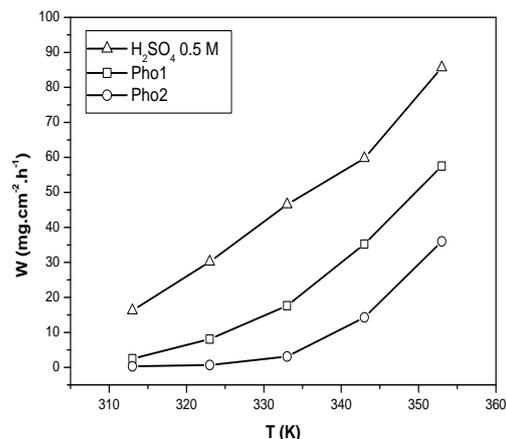

**Figure 5.** Variation of corrosion rate with temperature of steel at 10<sup>-3</sup> M of inhibitors.

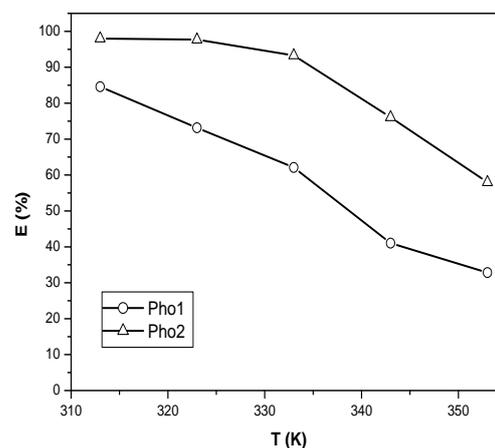

**Figure 6:** Variation of inhibition efficiency with temperature of steel at 10<sup>-3</sup> M of inhibitors.

The activation parameters for the corrosion process were calculated from Arrhenius type plot according to the following:

$$C_R = A \exp\left(-\frac{E_a}{RT}\right) \quad (8)$$

Where  $E_a$  is the apparent activation corrosion energy, T is the absolute temperature, A is the Arrhenius pre-exponential constant and R is the universal gas constant.


And the alternative formulation of Arrhenius equation is:

$$C_R = \frac{RT}{Nh} \exp\left(\frac{\Delta S_a^\circ}{R}\right) \exp\left(-\frac{\Delta H_a^\circ}{RT}\right) \quad (9)$$

Where h is Planck's constant, N is Avagadro's number,  $\Delta S_a$  is the entropy of activation and  $\Delta H_a$  is the enthalpy of activation.

Arrhenius plots for the corrosion rate of steel are given in (Figure 7). Values of ( $E_a$ ) for steel in 0,5M

H<sub>2</sub>SO<sub>4</sub> without and with optimum concentrations of Pho1 and Pho2 were calculated by linear regression between Ln (C<sub>R</sub>) and 1/T.

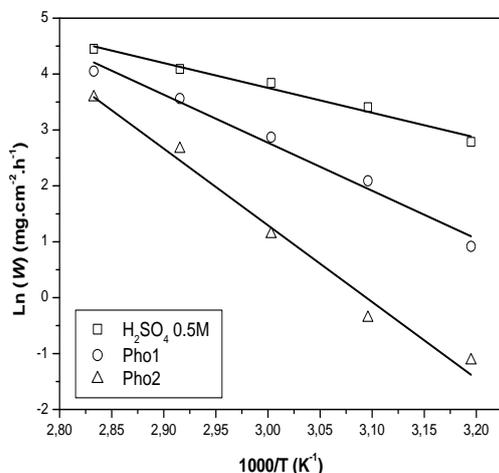

**Figure 7:** Arrhenius plots of steel for 10<sup>-3</sup> M of Pho1 and Pho2 in 0.5M H<sub>2</sub>SO<sub>4</sub>


Results are shown in (Table 5). All the linear regression coefficients are close to 1. The decrease of inhibition efficiencies with increasing temperature and the increase of E<sub>a</sub> in the presence of the inhibitor indicate the physical adsorption mechanism [30].

The figure 8 shows the variation of Ln (C<sub>R</sub>/T) function (1/T) as a straight line with a slope of (-H<sub>a</sub> / R) and the intersection with the y-axis is [Ln(R/Nh) + (ΔS<sub>a</sub> / R)]. From these relationships, values of ΔS<sub>a</sub> and ΔH<sub>a</sub> can be calculated. The activation parameters (E<sub>a</sub>, ΔH<sub>a</sub> and ΔS<sub>a</sub>) calculated from the slopes of Arrhenius lines in the absence and presence of our inhibitors (Fig.7 and Fig.8) are summarized in Table 5.

Inspection of these data reveals that the ΔH<sub>a</sub> values for dissolution reaction of steel in 0,5M H<sub>2</sub>SO<sub>4</sub> in the presence of inhibitors are higher than that of the absence of inhibitors. The positive signs of ΔH<sub>a</sub> reflect the endothermic nature of the steel dissolution process suggesting that the dissolution of steel is slow in the presence of inhibitors [31].

Moreover, for all systems, the average value of the difference between E<sub>a</sub> and ΔH<sub>a</sub> is about 2.87 kJ mol<sup>-1</sup> which approximately around the average value of RT (2.68 kJ mol<sup>-1</sup>).

$$E_a - \Delta H_a = RT \quad (10)$$

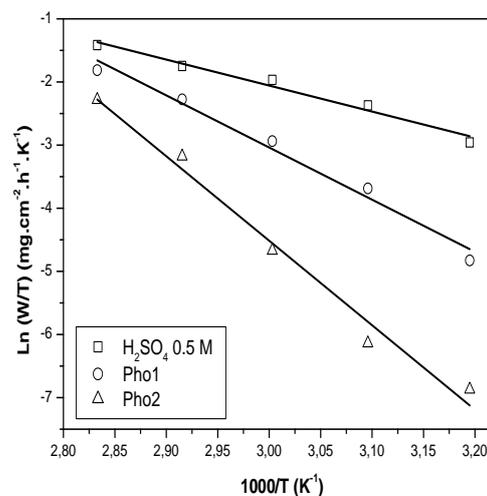

**Figure 8:** Plots of ln(C<sub>R</sub>/T) against T<sup>-1</sup> for 10<sup>-3</sup> of Pho1 and Pho2 in 0.5M H<sub>2</sub>SO<sub>4</sub>

**Table 5.** Values of activation parameters (E<sub>a</sub>, ΔH<sub>a</sub>, ΔS<sub>a</sub>) for steel in 0.5M H<sub>2</sub>SO<sub>4</sub> in the absence and presence of Pho1 and Pho2.

	R <sup>2</sup>	E <sub>a</sub> (kJ/mol)	ΔH <sub>a</sub> (kJ/mol)	ΔS <sub>a</sub> (J/mol.K)
Blank	0.978	37.1	34.23	-111.8
Pho1	0.982	71.41	68.65	-16.68
Pho2	0.984	114.05	111.25	98.83

On comparing the values of the entropy of activation (ΔS<sub>a</sub>) in (Table 5), it is clear that ΔS<sub>a</sub> is more positive in presence of the studied surfactant inhibitor compared to free acid solution. The increase of ΔS<sub>a</sub> in the presence of inhibitors implies that the activated Pho1 and Pho2 in the rate determining step represent an association rather than a dissociation step [32].


### 3.4. Adsorption isotherm and thermodynamic parameter

Adsorption isotherms are usually used to describe the adsorption process. The establishment of adsorption isotherms that describe the adsorption of a corrosion inhibitor can provide important clues to the nature of the metal-inhibitor interaction. Adsorption of the organic molecules occurs as the interaction energy between molecule and metal surface is higher than that between the H<sub>2</sub>O molecule and the metal surface [33]. The best correlation between the experimental results and isotherm functions was obtained using the Langmuir adsorption isotherm intercepted by the following equation:

$$\frac{C}{\theta} = \frac{1}{k} + C \quad (11)$$

Where C is the inhibitor concentration, K is the equilibrium constant and  $\theta$  is the surface coverage. From the values of surface coverage, the linear regressions between  $C/\theta$  and C are calculated by computer, and the parameters of adsorption are listed in Table 6. Figure 9 shows the relationship between  $C/\theta$  and C at 308 K. these results indicate that the adsorption of inhibitor onto steel surface agrees the Langmuir adsorption isotherm.

The obtained values of  $\Delta G_{ads}^{\circ}$  show a good correlation among thermodynamic parameters; those results ensure the spontaneity of the adsorption process and the stability of the adsorbed layer on the steel surface as well as strong interaction between the inhibitors and the metal surface [34].

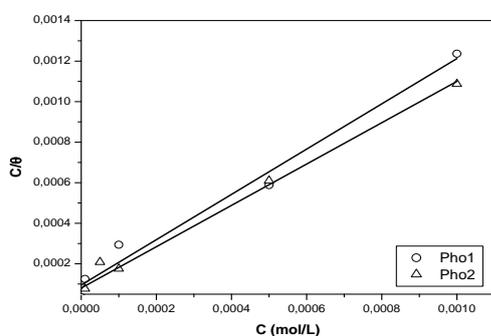

**Figure 9.** Langmuir adsorption isotherm of Pho1 and Pho2 on steel in 0.5M H<sub>2</sub>SO<sub>4</sub> at 308 K.

**Table 6.** Adsorption parameters of the linear regression between  $C/\theta$  and C of Pho1 and Pho2

Inhibitor	(R <sup>2</sup> )	$\Delta G_{ads}^{\circ}$ (kJ/mol)
Pho1	0.9822	-33.85
Pho2	0.9871	-34.43

Table 6 shows the negative values of  $\Delta G_{ads}^{\circ}$  indicate the spontaneity of adsorption of the inhibitor molecules on the mild steel surface [35]. In general,  $\Delta G_{ads}^{\circ}$  values below  $-20 \text{ kJ mol}^{-1}$  are due to the physisorption of the inhibitor, whereas  $\Delta G_{ads}^{\circ}$  values above  $-40 \text{ kJ mol}^{-1}$  are attributed to the chemisorption of the inhibitor molecules on metal surface. The values of  $\Delta G_{ads}^{\circ}$  are  $-33.85 \text{ kJ mol}^{-1}$  and  $-34.43 \text{ kJ mol}^{-1}$  for Pho1 and Pho2, respectively. The calculated values of  $|\Delta G_{ads}^{\circ}|$  of Pho in H<sub>2</sub>SO<sub>4</sub> indicate that the adsorption mechanism of Pho1 and Pho2 on mild steel involves both chemisorption and physisorption [36-38]. Owing to the adsorbed water molecules on the surface of mild steel, it may be assumed that the adsorption occurs first due to the electrostatic interaction, and then the removal of water molecules

from the surface is accompanied by chemical interaction between the metal surface and the adsorbate [39-42]. Moreover, the value of  $\Delta G_{ads}^{\circ}$  for Pho2 is lower than that for Pho1, further demonstrating that Pho2 exhibits the stronger tendency to adsorb on metal surface.

#### IV. CONCLUSION

Two phosphonate derivatives of Pho1 and Pho2 are good inhibitors for the corrosion of mild steel in 0,5M H<sub>2</sub>SO<sub>4</sub> solution.  $\eta$  increases with the inhibitor concentration but decreases with temperature. Both Pho1 and Pho2 act as mixed-type inhibitors. EIS spectra exhibit a large capacitive loop at high frequencies followed by a small inductive loop at low frequency values. The presence of inhibitor in 0,5M H<sub>2</sub>SO<sub>4</sub> solutions increases  $R_t$  while reduces  $C_{dl}$ . The value of apparent activation energy ( $E_a$ ) in the presence of inhibitors are higher than that in the absence of inhibitor.

#### REFERENCES

- [1] T. Poornima, N. Jagannatha, S.A. Nityananda, "Studies on Corrosion of Annealed and Aged 18 Ni 250 Grade Maraging Steel in Sulphuric Acid Medium". *Port. Electrochim.Acta*, 28(3), 2010, 173-188.
- [2] P. Kumar, A.N.S.hetty, "Electrochemical investigation on the corrosion of 18%Ni M250 grade maraging steel under welded condition in sulfuric acid medium" *Surf. Eng. Appl. Electrochem.*, 49(3), 2013, 253-260.
- [3] R. Javahrcdashti, "How corrosion affects industry and life", *Anti-corros. Methods Mater.*,47(1), 2000, 30 – 34.
- [4] G. TrabANELLI, "Inhibitors—An Old Remedy for a New Challenge", *Corrosion*, 47(6), 1991, 410-419.
- [5] A. Amin, M. Ibrahim, "Corrosion and corrosion control of mild steel in concentrated H<sub>2</sub>SO<sub>4</sub> solutions by a newly synthesized glycine derivative", *Corros Sci.*, 53(3), 2011, 873–885.
- [6] A. Ishtiaque, P. Rajendra, M.A. Quaraoishi, "Thermodynamic, electrochemical and quantum chemical investigation of some Schiff bases as corrosion inhibitors for mild steel in hydrochloric acid solutions", *Corros. Sci.*, 53(3), 2010, 933-942.
- [7] M.J. Bahrami, S.M.A. Hosseini, P. Pilvar, "Experimental and theoretical investigation of organic compounds as inhibitors for mild steel corrosion in sulfuric acid medium", *Corros Sci.*, 52(9), 2010, 2793–2803.

- [8] M.A. Hegazy, H.M. Ahmed, A.S. El-Tabei, "Investigation of the inhibitive effect of p-substituted 4-(N,N,N-dimethyldodecylammonium bromide)benzylidene-benzene-2-yl-amine on corrosion of carbon steel pipelines in acidic medium", *Corros. Sci.*, 53(2), 2011, 671-678.
- [9] A. Ouchrif, M. Zegmout, B. Hammouti, A. Dafali, M. Benkaddour, A. Ramdani, S. Elkadiri, "New synthesised diamine derivatives as corrosion inhibitors of steel in 0.5 M H<sub>2</sub>SO<sub>4</sub>", *Progress in Organic Coatings*, 53(4), 2005, 292-296.
- [10] N. Dkhireche, R. Abdelhadi, M. EbnTouhami, H. Oudda, R. Tourir, M. Elbakri, M. Sfaira, B. Hammouti, O.Senhaji, R. Taouil, "Elucidation of Dimethyldodecylphosphonate and CTAB Synergism on Corrosion and Scale Inhibition of Mild Steel in Simulated Cooling Water System", *Int. J. Electrochem.*, 7(6), 2012, 5314 - 5330.
- [11] O. Senhaji, R. Taouil, M.K. Skalli, M. Bouachrine, B. Hammouti, M. Hamidi, S.S. Al-Deyab, "Experimental and Theoretical Study for Corrosion Inhibition in Normal Hydrochloric Acid Solution by Some New Phosphonated Compounds", *Int. J. Electrochem. Sci.*, 6(12), 2011, 6290 - 6299.
- [12] R. Tourir, N. Dkhireche, M. EbnTouhami, M. Sfaira, O. Senhaji, J.J. Robin, B. Boutevind, M. Cherkaoui, "Study of phosphonate addition and hydrodynamic conditions on ordinary steel corrosion inhibition in simulated cooling water", *Mater. Chem. Phys.*, 122(1), 2010, 1-9.
- [13] F. Bentiss, C. Jama, B. Mernari, H. El Attari, L. EL Kadi, M. Lebrini, M. Traisnel, M. Lagrenée, "Corrosion control of mild steel using 3,5-bis(4-methoxyphenyl)-4-amino-1,2,4-triazole in normal hydrochloric acid medium" *Corros. Sci.*, 51(8), 2009, 1628-1635.
- [14] H. Amar, T. Braisaz, D. Villemin, B. Morceau, "Thiomorpholin-4-ylmethylphosphonic acid and morpholin-4-methylphosphonic acid as corrosion inhibitors for carbon steel in natural seawater" *Mater. Chem. Phys.*, 110(1), 2008, 1-6.
- [15] D. Gopi, K.M. Govindaraju, L. Kavitha, "Investigation of triazole derived Schiff bases as corrosion inhibitors for mild steel in hydrochloric acid medium" *J. Appl. Electrochem.*, 40(7), 2010, 1349-1356.
- [16] K.F. Khaled, K. Babic-Samardzija, N. Hackerman, "Cobalt(III) complexes of macrocyclic-bidentate type as a new group of corrosion inhibitors for iron in perchloric acid" *Corros. Sci.*, 48(10), 2006, 3014-3034.
- [17] F. Bentiss, M. Lebrini, M. Lagrenée, "Thermodynamic characterization of metal dissolution and inhibitor adsorption processes in mild steel/2,5-bis(n-thienyl)-1,3,4-thiadiazoles/hydrochloric acid system", *Corros. Sci.*, 47(12), 2005, 2915-2931.
- [18] M. Benabdellah, A. Dafali, B. Hammouti, A. Aouniti, M. Rhomari, A. Raada, O. Senhaji, J.J. Robin, "The role of phosphonate derivatives on the corrosion inhibition of steel in hcl media", *Chem. Eng. Commun.*, 194(10),2007, 1328-1341.
- [19] B. Yactine, F. Ganachaud, O. Senhaji, B. Boutevin, "Facile Manufacture and Storage of Poly(methylhydrogenosiloxane)s", *Macromolecules.*, 38(6), 2005, 2230-2236.
- [20] O. Senhaji, J.J. Robin, M. Achchoubi, B. Boutevin, "Synthesis and Characterization of New MethacrylicPhosphonated Surface Active Monomer", *Macromol. Chem. Phys.*, 205(8), 2004, 1039-1050.
- [21] E.S. Ferreira, C. Giancomelli, F.C. Giancomelli, A. Spinelli, "Evaluation of the inhibitor effect of l-ascorbic acid on the corrosion of mild steel", *Mater. Chem. Phys.*, 83(1), 2004, 129-134.
- [22] A. Ouchrif, M. Zegmout, B. Hammouti, A. Dafali, M. Benkaddour, A. Ramdani, S. Elkadiri, "New synthesiseddiamine derivatives as corrosion inhibitors of steel in 0.5M H<sub>2</sub>SO<sub>4</sub>", *Progress in Organic Coatings*, 53(4), 2005, 292-296.
- [23] N. Labjar, M. Lebrini, F. Bentiss, N-E.Chihib, S. El Hajjaji, C.E. Jama, "Corrosion inhibition of carbon steel and antibacterial properties of amino tris-(methylenephosphonic acid)", *Mater. Chem. Phys.*, 119(1-2), 2010, 330-336.
- [24] M. Lagrenée, B. Mernari, M. Bouanis, M. Traisnel, F. Bentiss, "Study of the mechanism and inhibiting efficiency of 3,5-bis(4-methylthiophenyl)-4H-1,2,4-triazole on mild steel corrosion in acidic media", *Corros. Sci.*, 44(3), 2002, 573-588.
- [25] A. K. Singh, M.A. Quraishi, "Effect of Cefazolin on the corrosion of mild steel in HCl solution" *Corros. Sci.*, 52(1), 2010, 152-160.
- [26] M. Lebrini, M. Lagrenée, H. Vezin, M. Traisnel, F. Bentiss, "Experimental and theoretical study for corrosion inhibition of mild steel in normal hydrochloric acid solution by some new macrocyclic polyether compounds", *Corros. Sci.*, 49(5), 2007, 2254-2269.

- [27] O. Benali, L. Larabi, M. Traisnel, L. Gengembre, Y. Harek, "Electrochemical, theoretical and XPS studies of 2-mercapto-1-methylimidazole adsorption on carbon steel in 1 M HClO<sub>4</sub>", *Applied Surface Science*, 253(14), 2007, 6130-6139.
- [28] E. McCafferty, N. Hackerman, "Double Layer Capacitance of Iron and Corrosion Inhibition with PolymethyleneDiamines" *J. Electrochem. Soc.*, 119(2), 1972, 146-154.
- [29] S. Muralidharan, K.L.N. Phani, S. Pitchumani, S. Ravichandran, S.V.K. Iyer, "Polyamino-Benzoquinone Polymers: A New Class of Corrosion Inhibitors for Mild Steel", *J. Electrochem. Soc.*, 142(5), 1995, 1478-1483.
- [30] A. Popova, E. Sokolova, S. Raicheva, M. Christov, "AC and DC study of the temperature effect on mild steel corrosion in acid media in the presence of benzimidazole derivatives", *Corros. Sci.* 45(1), 2003, 33-58.
- [31] N.M. Guan, L. Xueming, L. Fei, "Synergistic inhibition between o-phenanthroline and chloride ion on cold rolled steel corrosion in phosphoric acid", *Mater. Chem. Phys.*, 86(1), 2004, 59-68.
- [32] A.A. El-Awady, B.A. Abd-El-Nabey, S.G. Aziz, "Kinetic-thermodynamic and adsorption isotherms analyses for the inhibition of the acid corrosion of steel by cyclic and open-chain amines", *J. Electrochem. Soc.*, 139(8), 1992, 2149-2154.
- [33] G. Moretti, G. Quartarone, A. Tassan, A. Zingales, "Inhibition of mild steel corrosion in 1N sulphuric acid through indole", *Mater. Corros.* 45(12), 1994, 641-647.
- [34] L. Tang, X. Li, L. Li, Q. Qu, G. Mu, G. Liu, "The effect of 1-(2-pyridylazo)-2-naphthol on the corrosion of cold rolled steel in acid media: Part 1: Inhibitive action in 1.0 M hydrochloric acid", *Mater. Chem. Phys.*, 94(2-3), 2005, 353-359.
- [35] M. Abdallah, "Rhodanineazosulpha drugs as corrosion inhibitors for corrosion of 304 stainless steel in hydrochloric acid solution" *Corros. Sci.*, 44(4), 2002, 717-728.
- [36] A. Yurt, G. Bereket, A. Kivrak, A. Balaban, B. Erk, "Effect of Schiff Bases Containing Pyridyl Group as Corrosion Inhibitors for Low Carbon Steel in 0.1 M HCl", *J. Appl. Electrochem.*, 35(10), 2005, 1025-1032.
- [37] A. M. Fekry, R. R. Mohamed, "Acetyl thiourea chitosan as an eco-friendly inhibitor for mild steel in sulphuric acid medium", *Electrochim. Acta*, 55(6), 2010, 1933-1939.
- [38] V.R. Saliyan, A.V. Adhikari, "Quinolin-5-ylmethylene-3-[[8-(trifluoromethyl)quinolin-4-yl]thio]propanohydrazide as an effective inhibitor of mild steel corrosion in HCl solution", *Corros. Sci.*, 50(1), 2008, 55-61.
- [39] L.M. Vračar, D.M. Dražić, "Adsorption and corrosion inhibitive properties of some organic molecules on iron electrode in sulfuric acid", *Corros. Sci.*; 44(8), 2002, 1669-1680.
- [40] A. Chetouani, M. Daoudi, B. Hammouti, T. Ben Hadda, M. Benkaddour, "Inhibition of pure iron by new synthesized tripyrazole derivatives in HCl solution", *Corros. Sci.*, 48(10), 2006, 2987-2997.
- [41] F.M. Donahue, K. Nobe, "Theory of Organic Corrosion Inhibitors Adsorption and Linear Free Energy Relationships" *J. Electrochem. Soc.*, 112(9), 1965, 886-891.
- [42] E. Khamis, F. Bellucci, R.M. Latanision, E.S.H. El-Ashry, "Acid Corrosion Inhibition of Nickel by 2-(Triphenylphosphorylidene) Succinic Anhydride", *Corrosion*, 47(9), 1991, 677-686.